



# **Potential Yucca Mountain Repository: the Materials Behavior in the Risk- informed Performance-based Evaluation**

**Tae M. Ahn  
Senior Materials Engineer  
U.S. Nuclear Regulatory Commission  
Washington, D.C. 20555-0001, U.S.A.**

# **Presented to**

- (1) Japan Nuclear Energy Safety Organization (JNES) and Central Research Institute of Electric Power Industry (CRIEPI), Tokyo, Japan, March 27, 2006**
- (2) Radioactive Waste Management Funding and Research Center (RMWC), Tokyo, Japan, March 28, 2006**
- (3) Nuclear Environmental Technology Center of Korea Hydro and Nuclear Power and Korea Atomic Energy Research Institute (KAERI), Daejeon, Korea, March 29, 2006**
- (4) Korea Institute of Nuclear Safety (KINS), Daejeon, Korea, March 29, 2006**

## **Disclaimer:**

**The NRC staff views expressed herein are preliminary and do not constitute a final judgment or determination of the matters addressed or of the acceptability of a license application for a geological repository at Yucca Mountain.**

# **PURPOSE**

- **Present U.S. Nuclear Regulatory Commission (NRC)'s risk-informed, performance-based evaluation of materials behavior in the potential licensing of the Yucca Mountain (YM) repository**
- **Present compliance assessment methods and tools for risk assessments, for operation safety, and for long-term waste isolation**
- **Present issues associated with waste form**
- **Present issues associated with waste package (WP) and drip shield (DS) materials**

# OUTLINE

- **The NRC's Evaluation of the Potential YM Repository of High-Level Waste (HLW)**
- **Schematic Illustration of the Potential YM Repository**
- **Compliance Assessment and Tools for Risk Assessment: operation safety, waste isolation**

# **OUTLINE (continued)**


- **Waste Form:**
  - initial cladding conditions
  - dose calculation for drop/collision and oxidation of spent nuclear fuel (SNF) assemblies
  - repository radionuclide release and dose calculation
  - rims, hydride embrittlement, Np solubility and Pu colloids
- **Canister, WP and DS:**
  - Transportation, Aging and Disposal (TAD) Canister
  - WP and DS – failure modes, localized corrosion, long-term passivity, materials stability, creep, fabrication reliability

# **Potential YM Repository of HLW**

**The NRC's evaluation includes:**

- (i) Construction and operation of the pre-closure facilities (i.e., safety)**
- (ii) Ability of the repository to isolate HLW (i.e., waste isolation)**


## Schematic Illustration of the Emplacement Drift with Cutaway Views of Different Waste Packages (DOE, 2002)

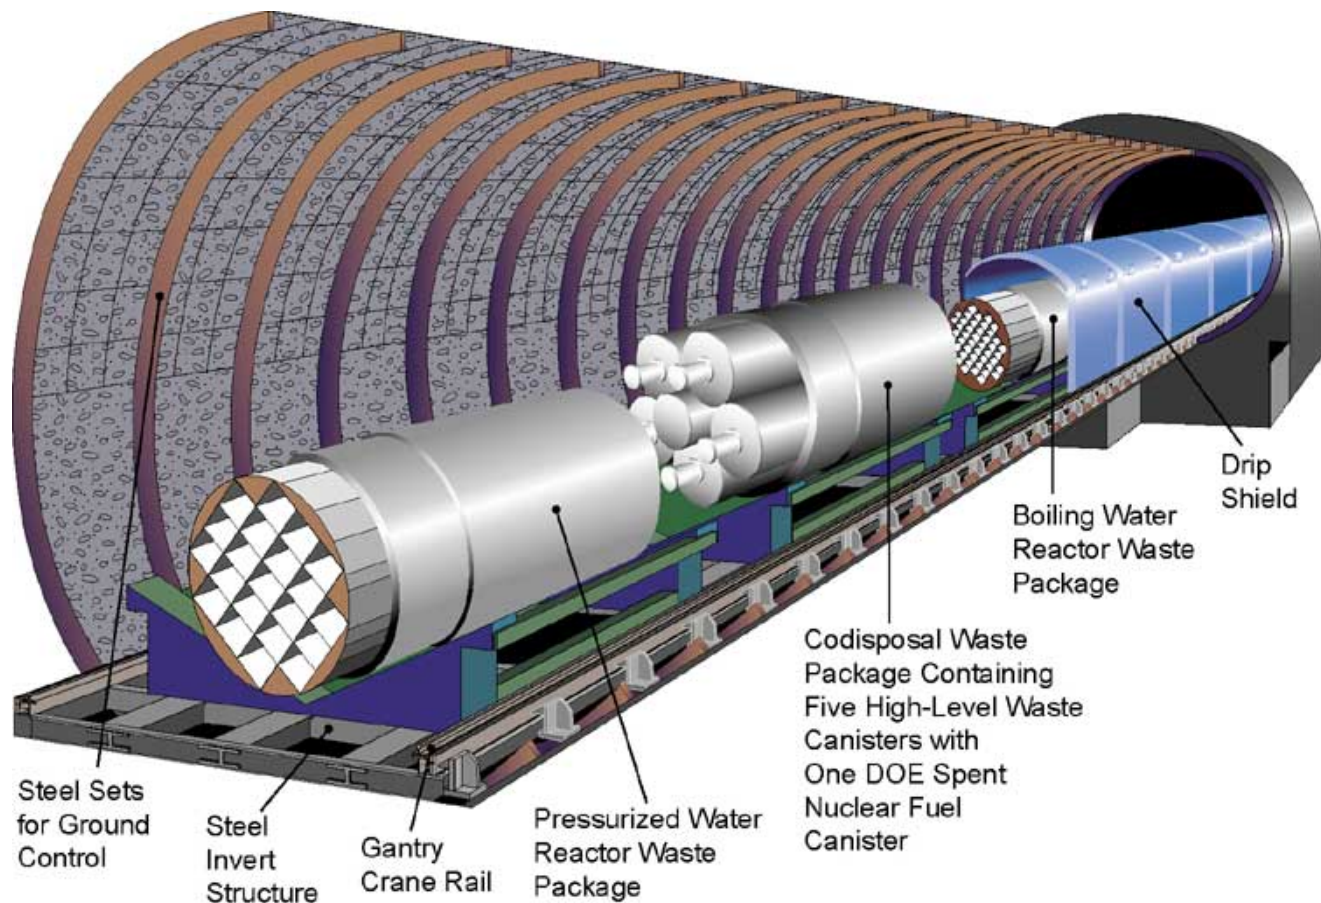


Drawing Not to Scale  
00022DC\_ATP\_Z1S30-02a.ai



## Proposed Monitored Geologic Repository Facilities at Yucca Mountain (DOE, 2002)

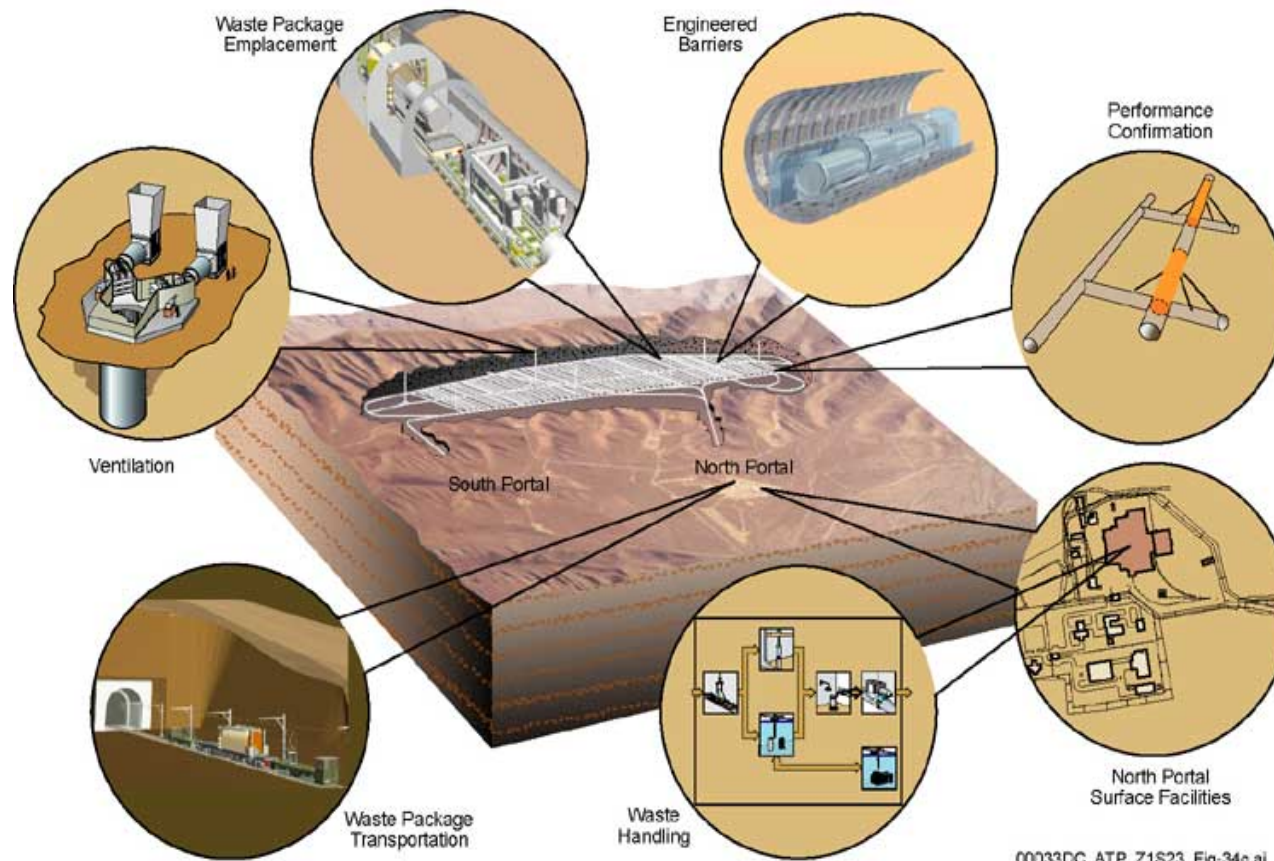

# Schematic Illustration of the Ten General Processes Considered and Modeled for Total System Performance Assessment (DOE, 2002)

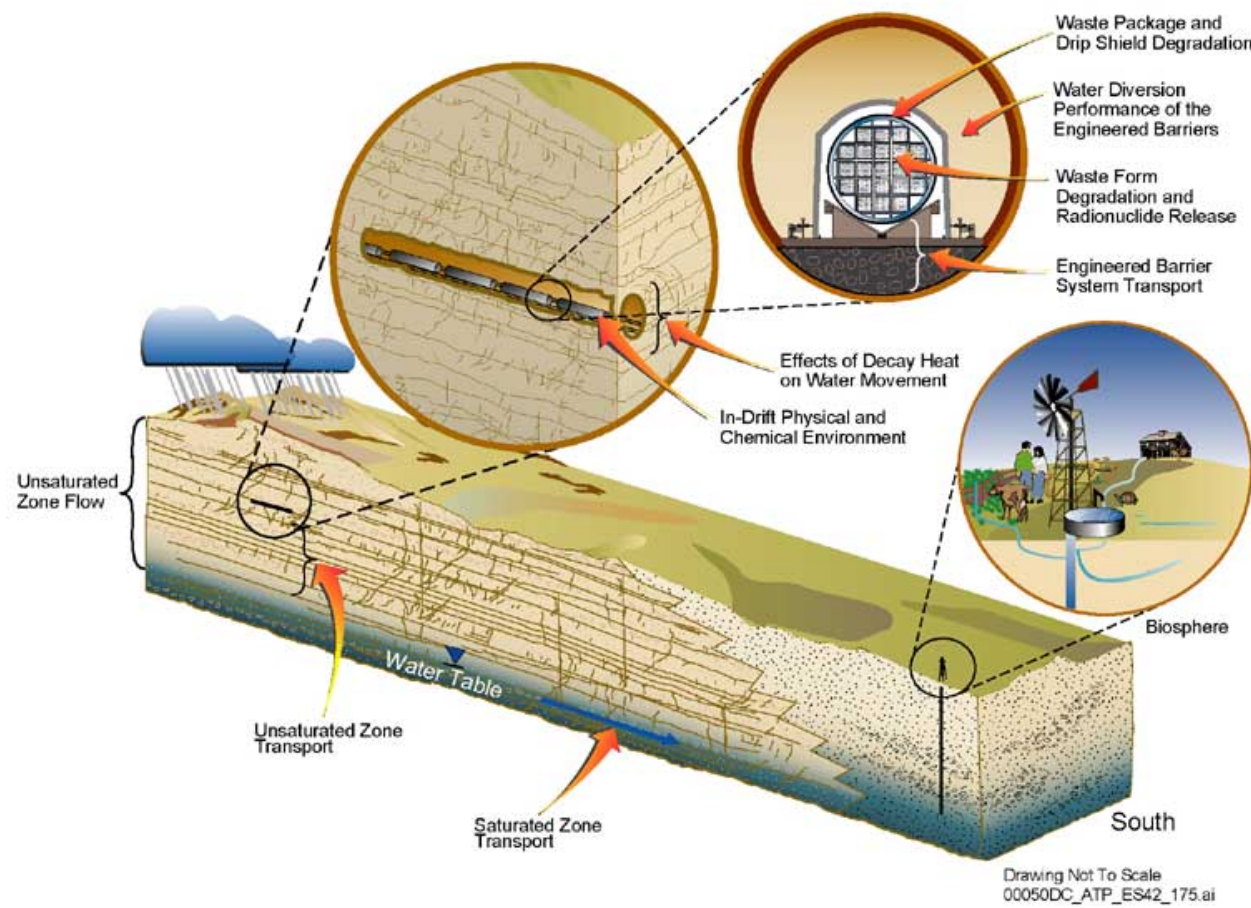

## View Looking Down Exploratory Studies Facility (DOE, 2002)



ATP\_Z1S1\_Fig1-15.ai



# **Compliance Assessment**


**The radionuclide releases must comply with the performance objectives (i.e., regulatory dose requirements)**

- (i) safety: for workers and the public under normal operating and accident conditions (e.g., drop/collision, power off, building leakage, seismicity, or aircraft crash)**
- (ii) waste isolation: for individual protection, human intrusion, and groundwater protection under nominal and disruptive (e.g., seismicity and volcanism) scenarios**

## **Tools for Risk Assessments**

- **Safety: Pre-Closure Safety Analysis (PCSA)**
  - initiating events and event sequences - annual probability cutoff
  - SNF assemblies at risk
  - fault and event tree probabilistic scheme
  - consequence models
  - bases for model supports
- **Waste Isolation: Total-system Performance Assessment (NRC's TPA, DOE's TSPA)**
  - screening of event sequences and scenarios – annual probability cut off
  - Monte Carlo scheme
  - consequence models – engineering, geology, and hydrology
  - bases for model supports

# Waste Form Inventory

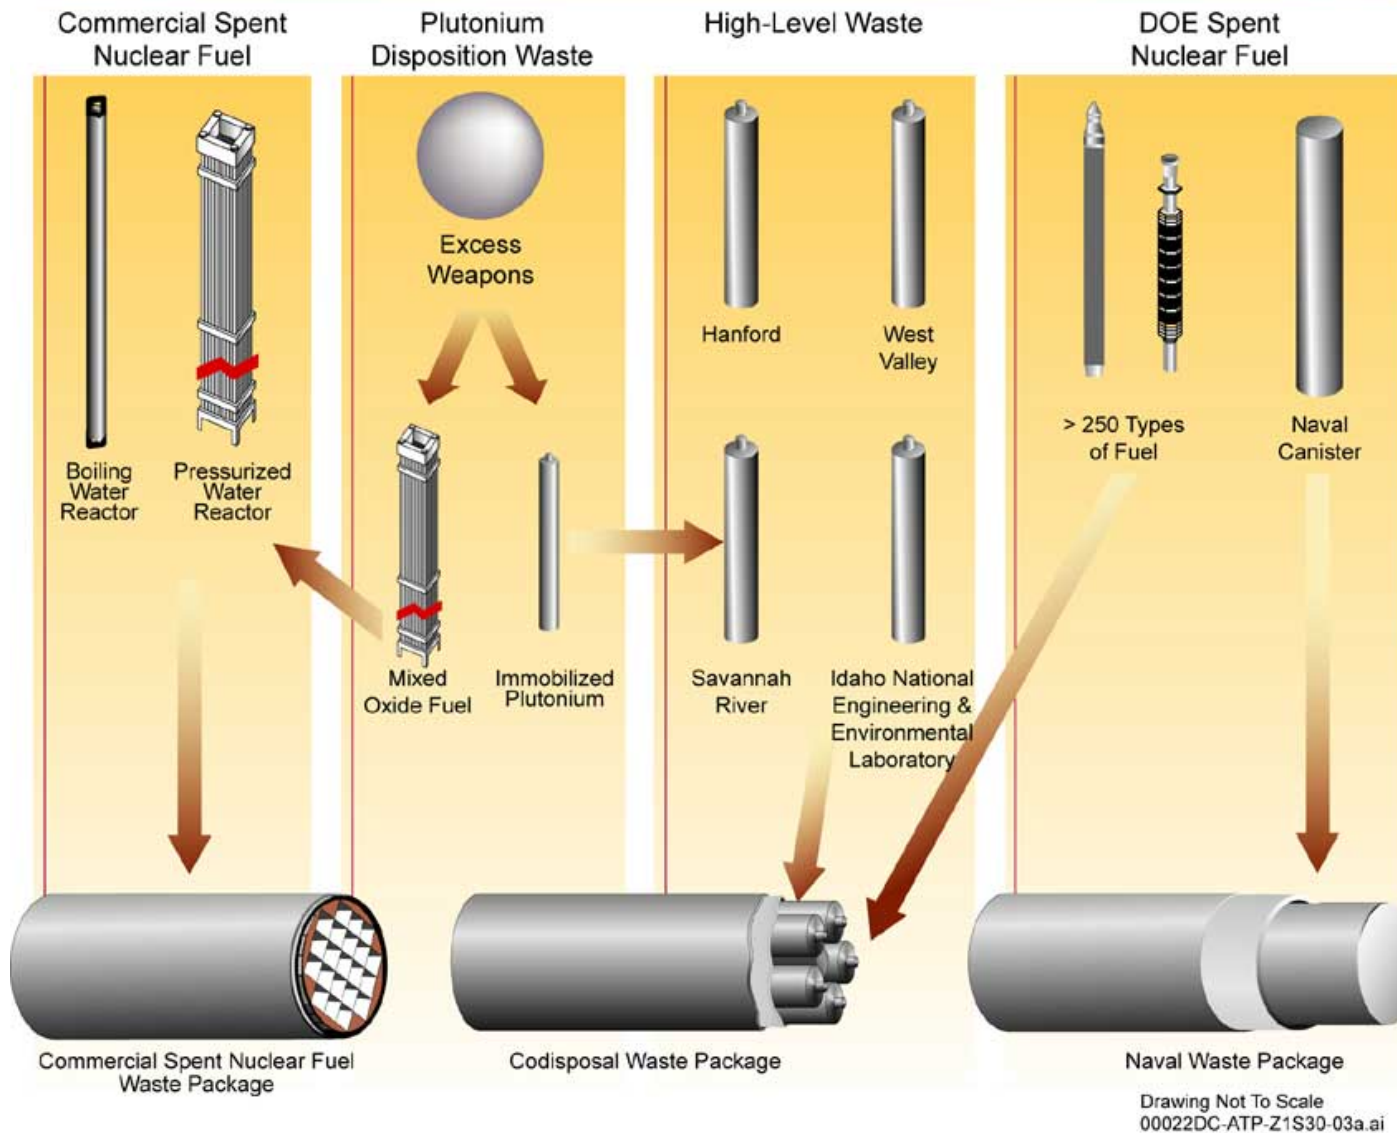

## **Initial Cladding Condition: pin-holes, hairline cracks, or rupture**

### **Safety:**

- **could be generated during the normal reactor operation; could be developed more and further during the subsequent handling operations, should the cladding have high stress, vibration or larger flaws, or is subject to embrittlement**
- **may lead to matrix oxidation should the SNF be exposed to oxygen at elevated temperatures, which may occur at SNF dried for loading. Partial oxidation potentially causes SNF pellets to crumble and generate respirable particulates upon vibration or any stress applied during transportation and storage.**
- **may lead to matrix oxidation should the SNF be exposed to oxygen at elevated temperatures, which may occur as SNF is transferred from transportation/staging packages to the disposal waste package at the potential pre-closure facilities**
- **methods for detecting pin-holes and hairline cracks and their sensitivity are being explored**

## **Waste Isolation:**

- **Failed waste packages (e.g., initially defective, corrosion or mechanical) may allow radionuclide releases from SNF rods with pin-holes and hairline cracks.**

**The grain boundary and gap radionuclide inventories are considered to be mobilized rapidly, whereas the matrix inventory is considered to be mobilized at the slow SNF dissolution rate.**


- **Effects of pin-holes and hairline cracks on release**

**No partial credit is given to cladding with pin-holes and hairline cracks or ruptured in DOE's TSPA – assumed to be bare SNF pellets without cladding**

- **SNF rods with pinholes and hairline cracks or ruptured may lead to reconfiguration for potential criticality.**




# Conceptual Model of Commercial Spent Nuclear Fuel Cladding Degradation (DOE, 2002)

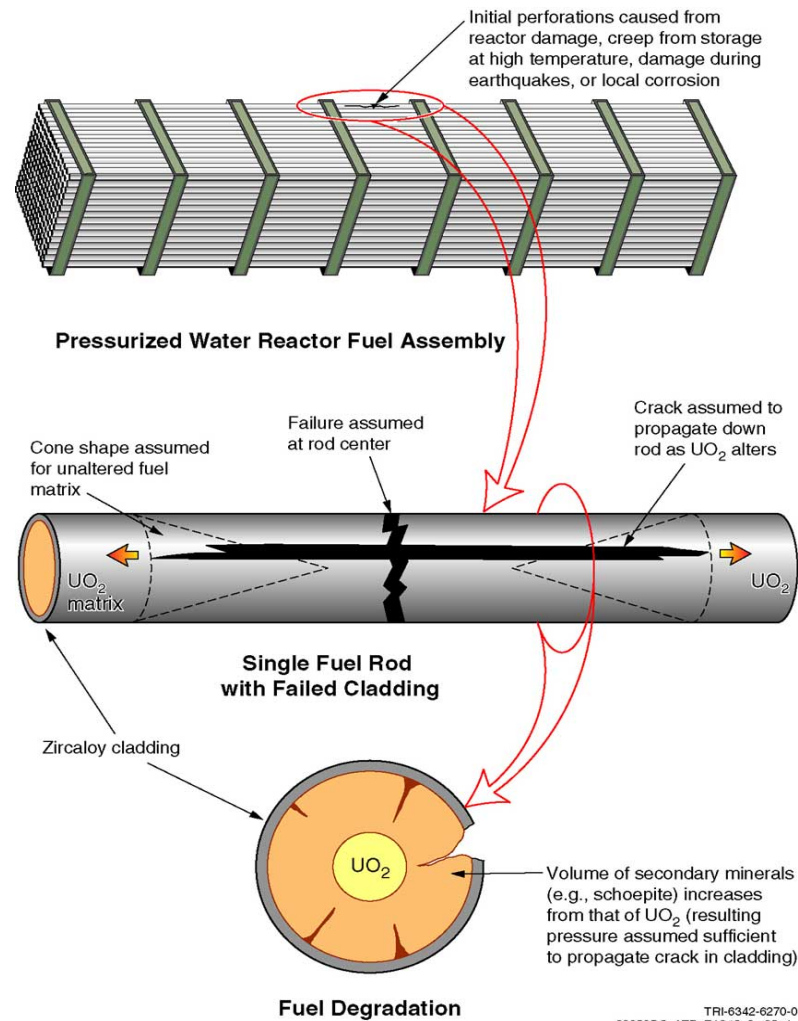


TRI-6342-6270-0  
00050DC\_ATP\_Z1S42\_fig-05.ai

# Example Dose Calculation Per SNF Assembly

(Kamas et al., 2005)

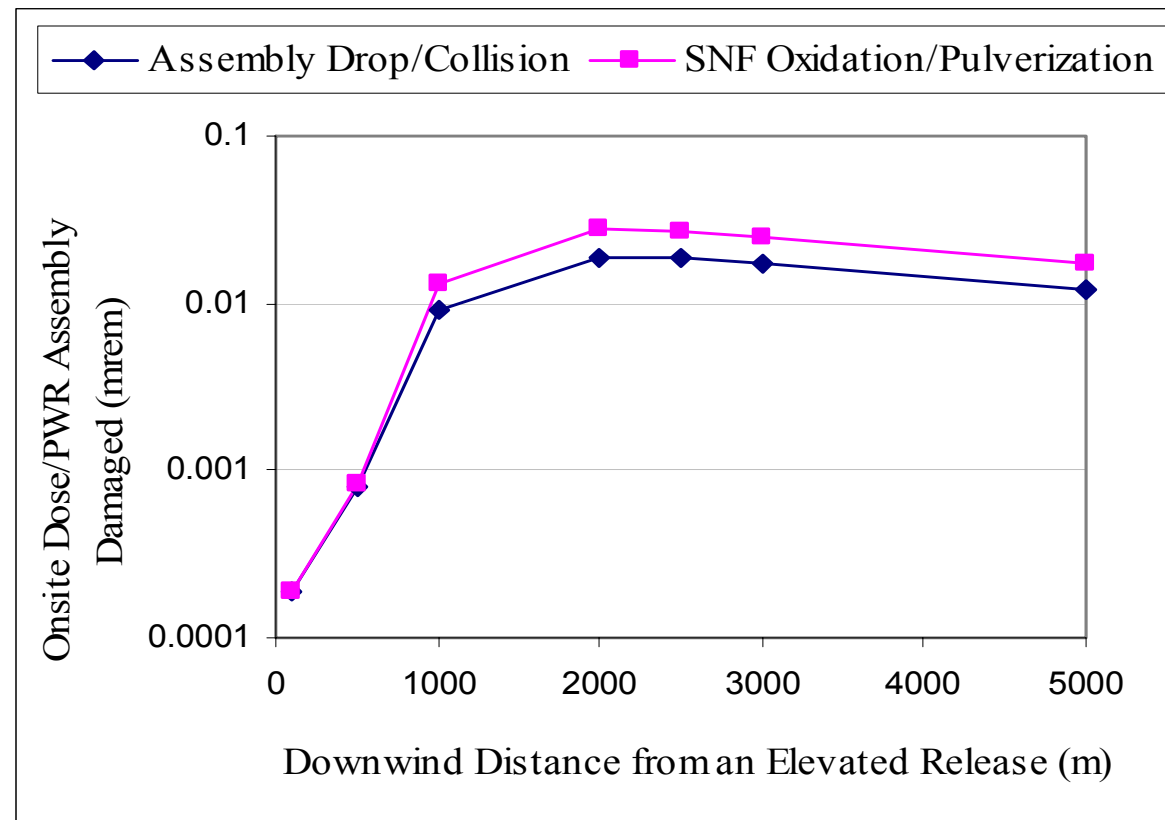

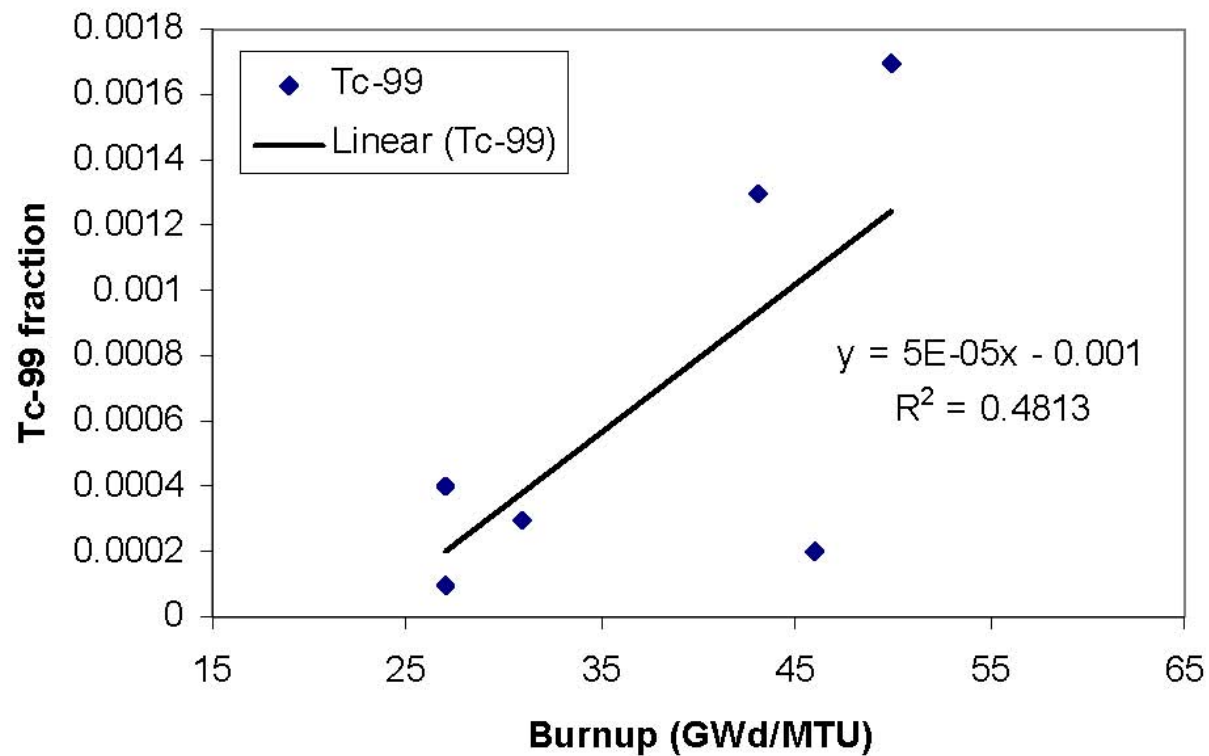


**Instant Release Fraction for Tc-99 As a Function of Burnup. Data Are Extracted from Johnson and Tait (1997). (50GWd/MTU =  $3.64 \times 10^{12}$  Btu/ton)**

**(From Jain et al., 2004)**

# Matrix Dissolution

- **Groundwater Contact Mode**
- **Cation**
- **pH**
- **Oxygen and Iron Concentration**
- **Temperature**
- **Prior Oxidation/Hydration**
- **Grain Boundary Inventory**
  
- **Partial Cladding Protection**
  - Slit ( $\sim 0.015$  cm [ $5.9 \times 10^{-3}$  in] dia. X  $\sim 2.54$  cm [1 in] length) -  
or Hole ( $\sim 0.02$  cm [ $7.9 \times 10^{-3}$  in] dia.) – Defective SNF rods Immersion  
Tests in J-13 Well Water at 85 °C (Wilson, 1990)
  - release decreased by a factor of  $\sim 140$  for Tc-99,  $\sim 7 \times 10^5$  for I-129  
and  $\sim 65$  for Sr-90

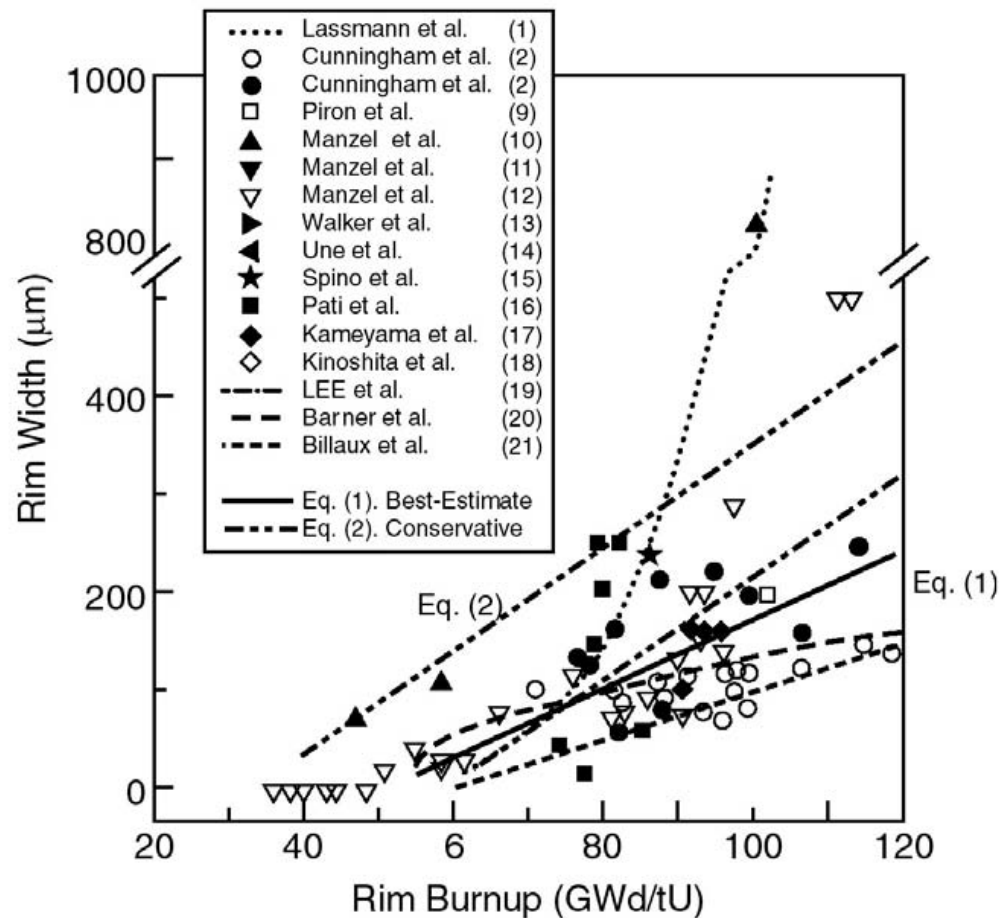


**Measured Rim Width Both by Electron Microprobe Analyzer and Optical Microscopy (Koo, et al., 2001). (Reproduced with Permission from Copyright Clearance Center). NOTE: Refer to Koo, et al. (2001) for Information on References Cited in the Figure.**

**(From Jain et al., 2004)**


# Hydride Reorientation – Creep Tests

- Radial hydrides, as little as 40 wppm, can significantly degrade cladding's mechanical properties. (Marshall)
- Stress, temperature, cool-down rate, microstructure, H content, etc., all play important roles. (Einziger)
  - Threshold hoop stress for 400°C is ~ 100 MPa.

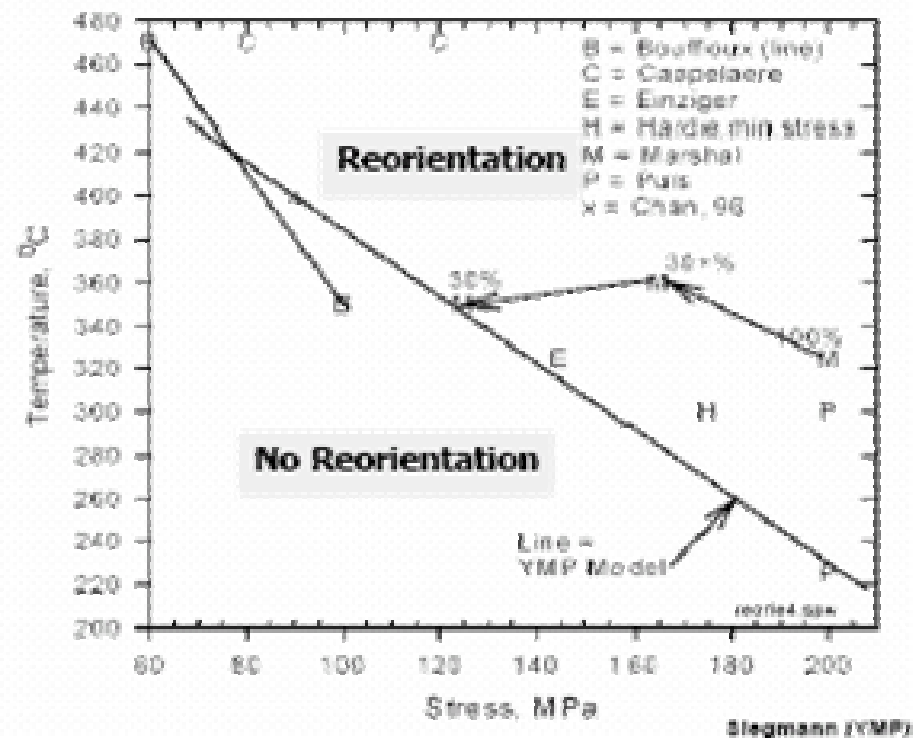


From Tsai, 2003 (1 MPa = 0.145 ksi; 200°C = 392 °F)


## Np Solubility (DOE, 2004)

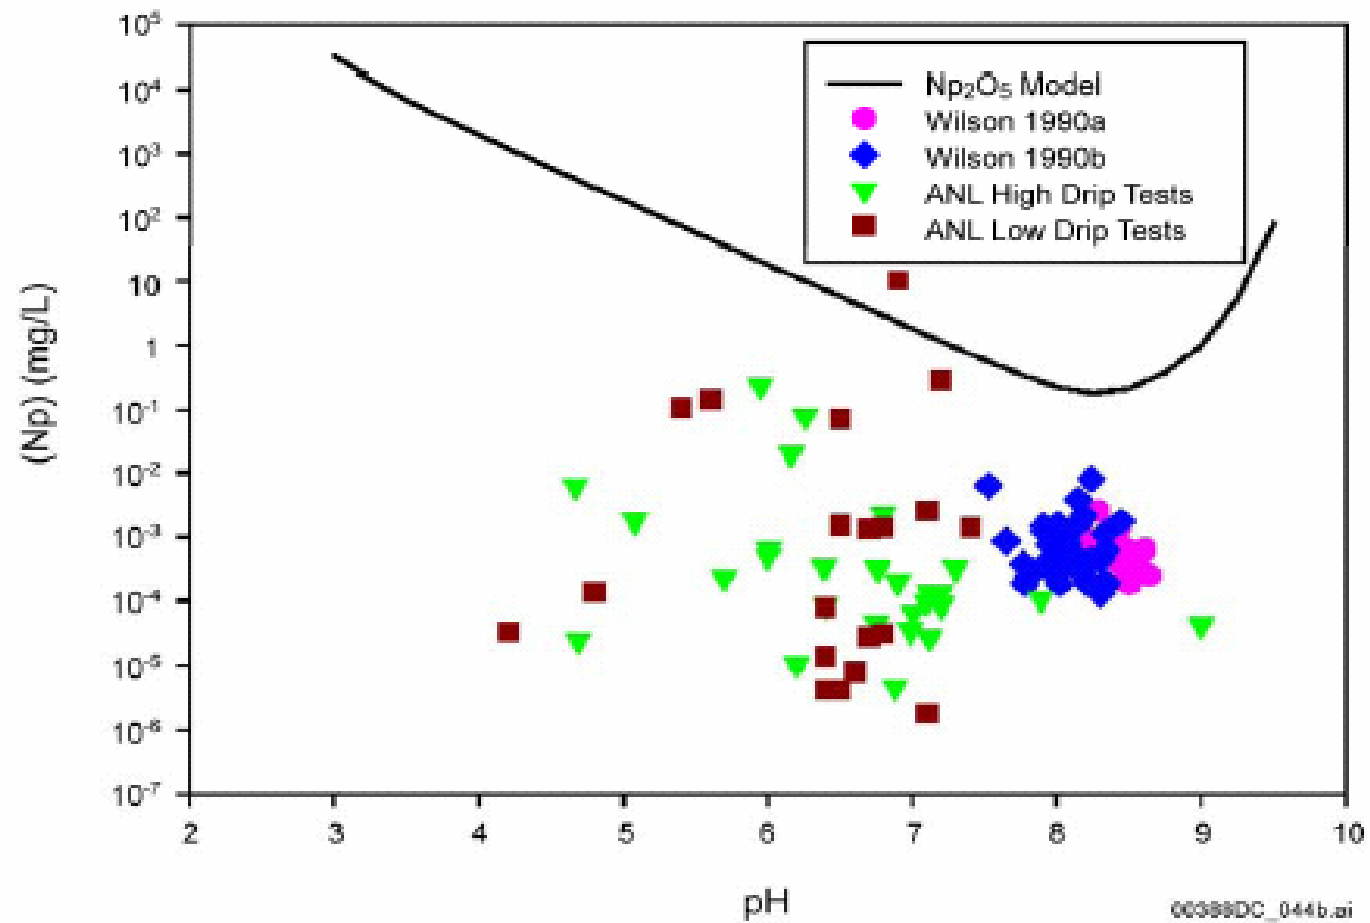

**Transmission Electron Microscopy (TEM) Micrographs of  
Particulate Material Isolated on a Holey Carbon TEM Grid:  
(a) Colloids Formed from Solution and (b) Material in Liquid  
Spalled from the Glass Surface (Bates et al., 1992)**

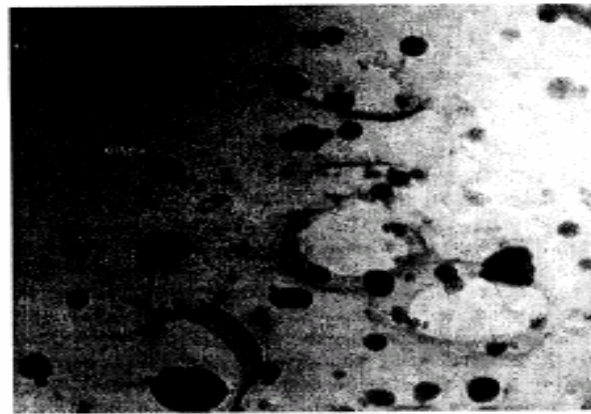

**(a)**

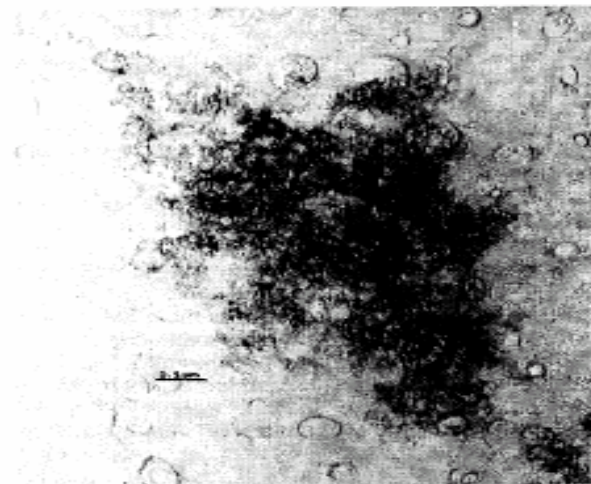

**(b)**



# Cladding Protection in Release (Mohanty et al., 2004)

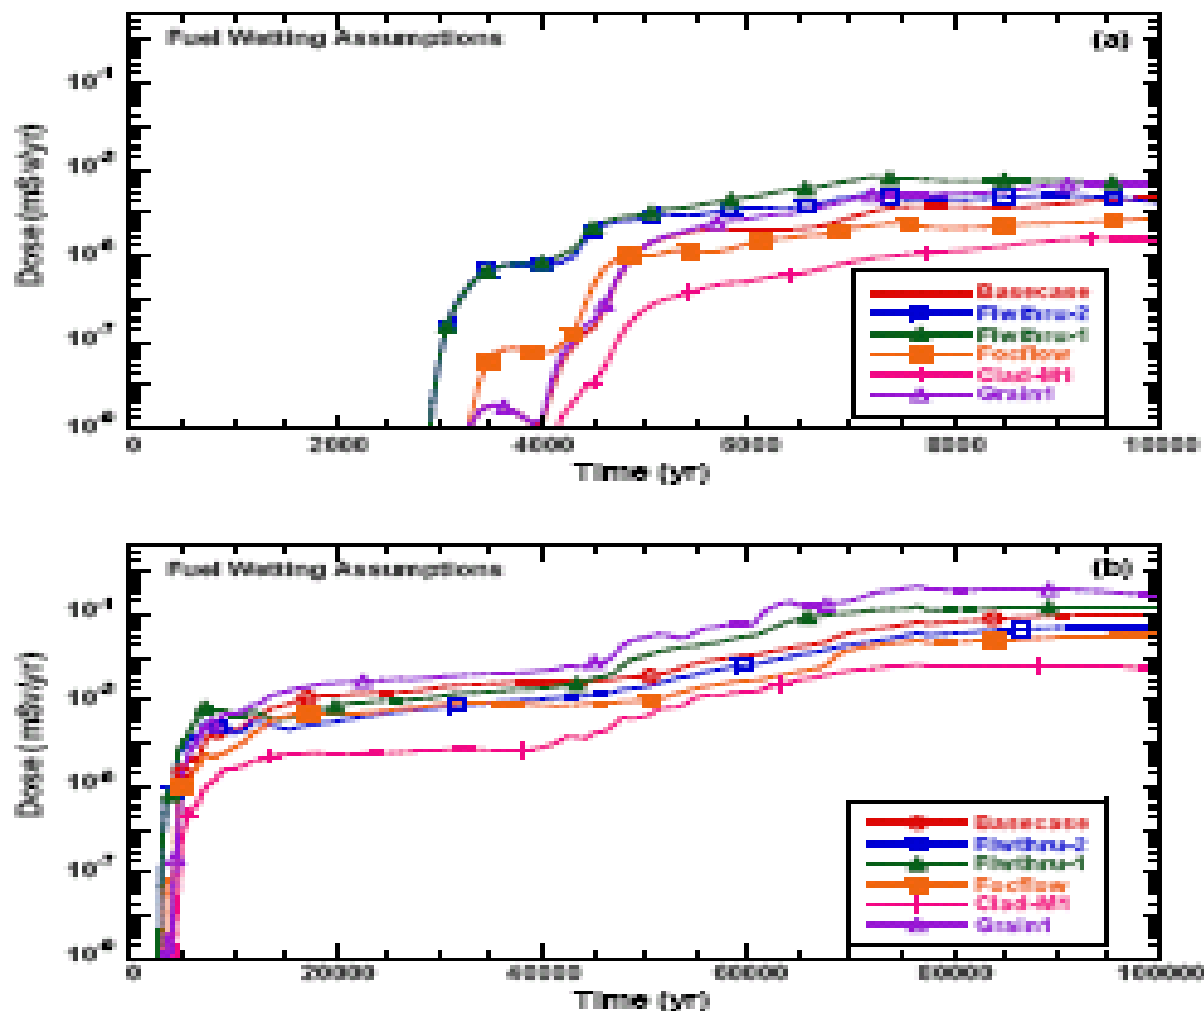


Figure 3-37. Average Groundwater Dose from the Basecase and the Fuel-Wetting Alternative Conceptual Models in (a) 10,000 and (b) 100,000 Years, for 350 Realizations

# **TAD Canister**

**DOE's Recently Proposed Conceptual Design  
using**

***Standardized Transportation, Aging and Disposal  
(TAD) Canisters***

# **Waste Package**

**(Alloy 22, Ni-22Cr-13.5Mo-3W-4Fe)**


- **Long-Term Passivity in Uniform Corrosion**
- **Localized Corrosion**
- **Stress Corrosion Cracking**
- **Long-Term Phase Stability**
- **Mechanical Failure**
- **Fabrication and Reliability**

# **Drip Shields**

## **(Ti-7 and Ti-24, Pd addition)**


- **Long-Term Passivity in Uniform Corrosion**
- **Fluoride Uniform Corrosion**
- **Hydride Embrittlement**
- **Stress Corrosion Cracking**
- **Creep**

# Localized Corrosion

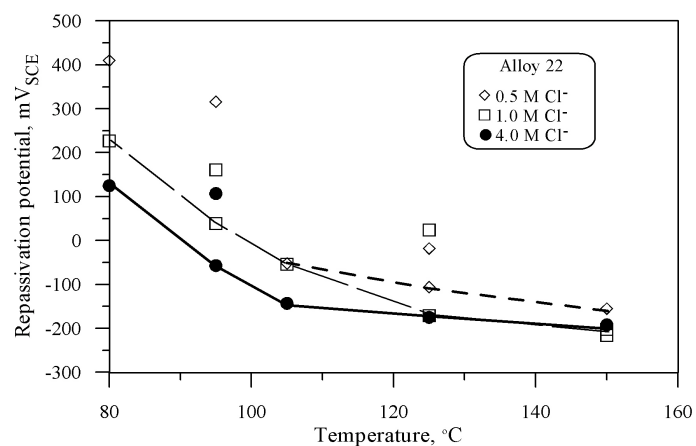

**Effect of temperature on the repassivation potential crevice corrosion of Alloy 22 in Cl<sup>-</sup> solutions (Brossia et al., 2001)**

(100 °C = 212 °F)

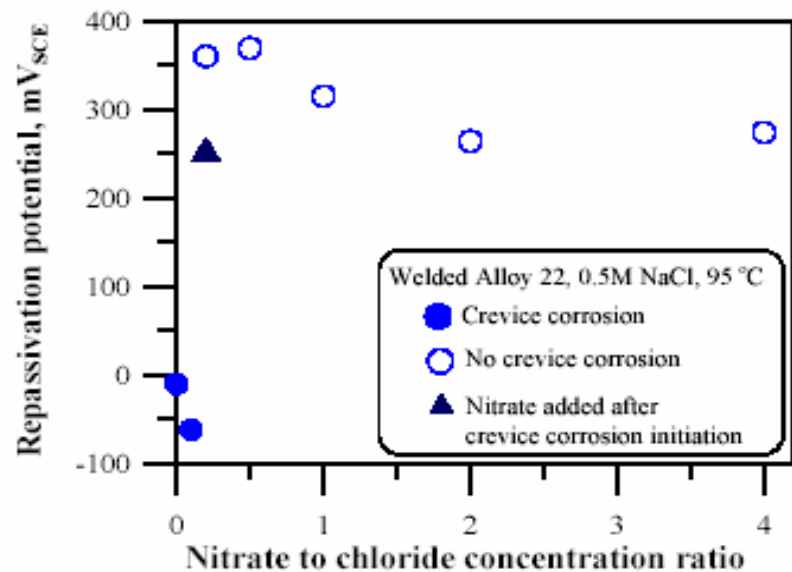


(Dunn et al., 2003)

# Uniform Corrosion

- **Data from DOE, CNWRA, industries and international community (e.g., long-term German tests in rocksalts) point out similarities of uniform corrosion rates. A container lifetime of greater than 10,000 years can be estimated.**
- **A long-term integrity of passive film is suggested by various models for point defects, chemistry segregation, and passive film growth.**
- **Analogue studies suggests that modern electrochemical theories for corrosion may explain the analogue observation: void formation, stoichiometric dissolution of meteorites and josephinite, possible passivity of Indian Pillar, and long-term passivity of carbon and stainless steel over half a century (Sridhar and Cragnolino, 2002).**

# Time-Temperature-Transformation Diagram for Alloy 22 Base Metal (DOE, 2002)

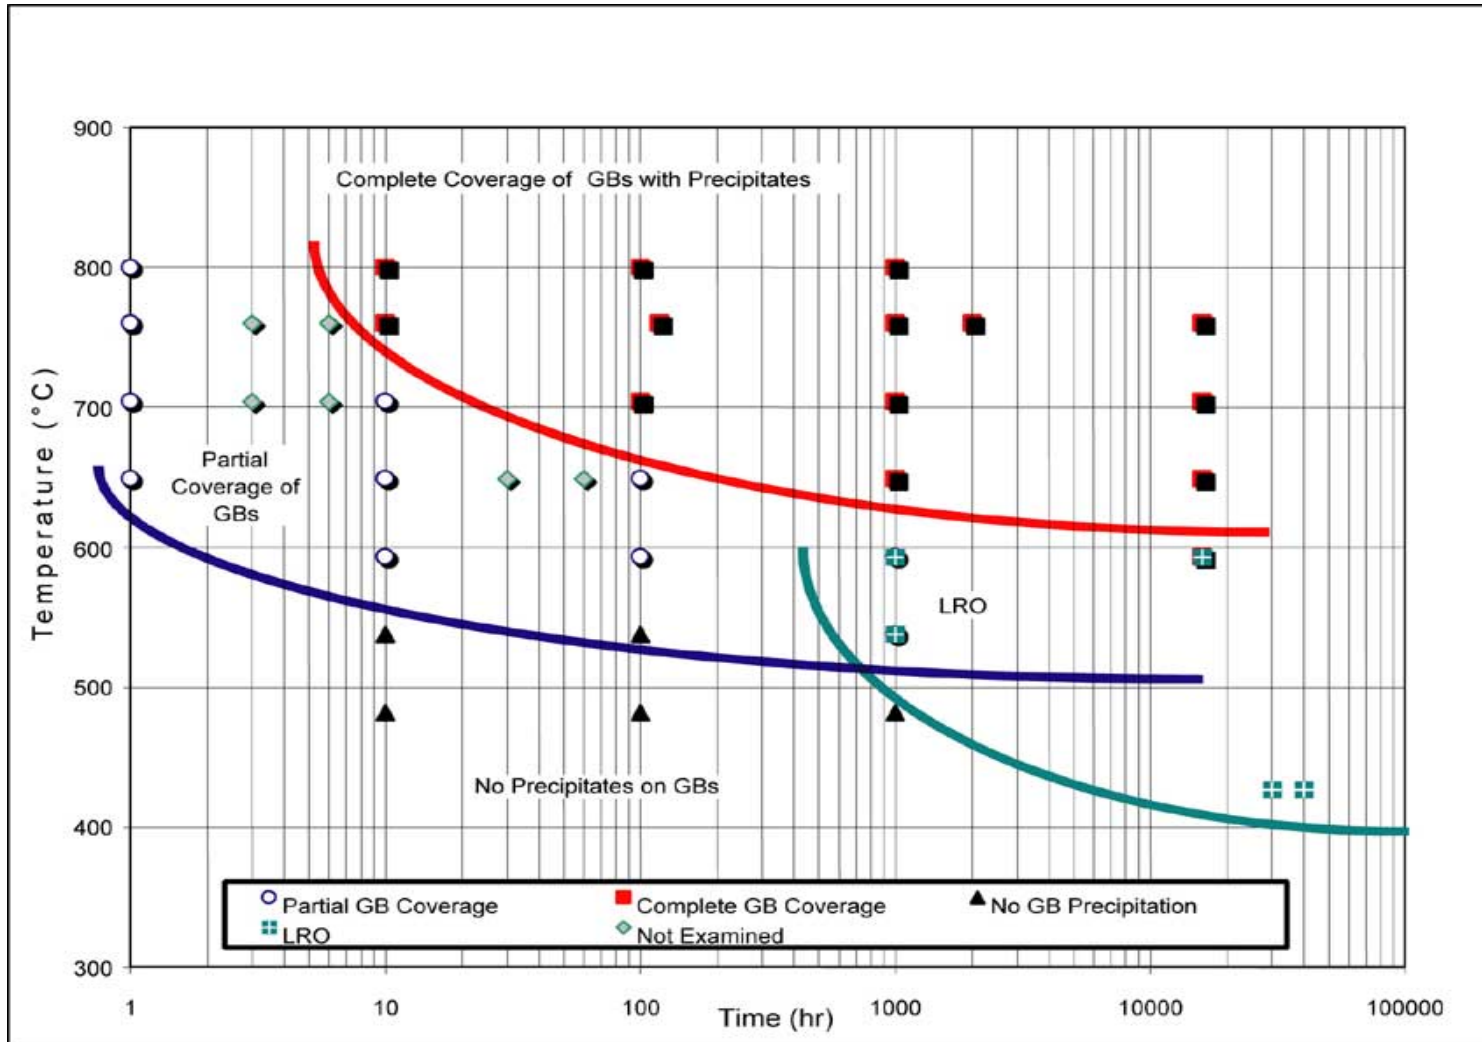

00050DC\_ATP\_Z1S42\_102.ai

# **Low-Temperature Drip Shield Creep**

**(Neuberger et al., 2002)**

- **Expected drip shield creep after rockfall loadings near material yield stress while drift operating temperatures are approximately 100 – 150° C**



## Metal Fabrication Reliability (Jain et al., 2003)

Table 4-1. Observed Weld Flaw Frequencies <sup>*†</sup>					
Vessel	Location	Size of Cracks	Weld Volume	Number of Flaws	Flaws/m <sup>3</sup> [flaws/ft <sup>3</sup> ]
Pressure Vessel Research User Facility	Near Surface Zone {25 mm [0.98 in]}	< 3 mm [< 0.12 in]	0.014 m <sup>3</sup> [0.49 ft <sup>3</sup> ]	191	13,571 [384.3]
	Near Surface Zone {25 mm [0.98 in]}	> 3 mm [> 0.12 in]	0.014 m <sup>3</sup> [0.49 ft <sup>3</sup> ]	13	929 [26.3]
	Remaining thickness	< 5 mm [< 0.20 in]	0.20 m <sup>3</sup> [0.7 ft <sup>3</sup> ]	653	3,625 [102.6]
	Remaining thickness	> 5 mm [> 0.20 in]	0.20 m <sup>3</sup> [0.7 ft <sup>3</sup> ]	27	135 [3.8]
Shoreham Reactor Pressure Vessel	Inner 25 mm [0.98 in] surface	< 4 mm [< 0.16 in]	0.0226 m <sup>3</sup> [0.8 ft <sup>3</sup> ]	459	20,309 [574.5]
	Inner 25 mm [0.98 in] surface	> 4 mm [> 0.16 in]	0.0226 m <sup>3</sup> [0.8 ft <sup>3</sup> ]	9	398 [11.3]
	Outer 25 mm [0.98 in] surface	< 4 mm [< 0.16 in]	0.0241 m <sup>3</sup> [0.85 ft <sup>3</sup> ]	639	26,515 [750.8]
	Outer 25 mm [0.98 in] surface	> 4 mm [> 0.16 in]	0.0241 m <sup>3</sup> [0.85 ft <sup>3</sup> ]	19	788 [22.3]
<sup>*</sup> Doctor, S.R., G.J. Schuster, and F.A. Simonen. NUREG/CP-0166, Vol. 1, "Fabrication Flaws in Reactor Pressure Vessels." Proceedings of the Twenty-Sixth Water Reactor Safety Information Meeting, Bethesda, Maryland, October 26-28, 1998. Washington, DC: NRC. pp. 85-103. June 1999. <sup>†</sup> Schuster, G.J., S.R. Doctor, S.L. Crawford, and A.F. Pardini. NUREG/CR-6471, Vol. 3, "Characterization of Flaws in U.S. Reactor Vessels—Density and Distribution of Flaw Indications in Shoreham Vessel." Washington, DC: NRC. November 1999.					

# References

- Bates, J. K. et al., ANL Technical Support Program for DOE Environmental Restoration and Waste Management: Annual Report – October 1990 – September 1991, ANL-92/9, Argonne National Laboratory, 1992, Argonne, IL
- Brossia, C. et al., Effect of Environment on the Corrosion of Waste Package and Drip Shield Materials, CNWRA 2001-03, Center for Nuclear Waste Regulatory Analyses, 2001, San Antonio, TX
- Dunn, D. S., D. Daruwalla and Y.-M. Pan, Effect of Fabrication Processes on Material Stability – Characterization and Corrosion, CNWRA 2004-01, Center for Nuclear Waste Regulatory Analyses, 2003, San Antonio, TX
- Jain, V., G. Cragnolino and L. Howard, A Review Report on High Burnup Spent Nuclear Fuel – Disposal Issues, CNWRA 2004-08, Center for Nuclear Waste Regulatory Analyses, 2004, San Antonio, TX
- Jain, V., D. Daruwalla and C. Fairbank, Assessment of Mechanisms for Early Waste Package Failures, CNWRA 2003-05, Center for Nuclear Waste Regulatory Analyses, 2003, San Antonio, TX
- Kamas, S., T. Ahn and M. Bailey, Pre-Closure Safety Analysis: Sensitivity Studies and Preliminary Dose Results, U.S. Nuclear Regulatory Commission, ADAMS: ML 052660199, 2005, and also submitted for presentation to International High-Level Radioactive Waste Management Conference, Las Vegas, NV, 2006
- Mohanty, S. et al., System-Level Performance Assessment of the Proposed Repository at Yucca Mountain using the TPA Version 4.1 Code, CNWRA 2002-05, Revision 1, Center for Nuclear Waste Regulatory Analyses, 2002, San Antonio, TX
- Neuberger, B. et al., Creep Analyses of Titanium Drip Shield Subjected to Rockfall Static Loads in the Proposed Geologic Repository at Yucca Mountain, Mat. Res. Soc. Symp. Proc., Vol. 713, p 97 – 104, 2002
- Sridhar, N. and C. Cragnolino, Evaluation of Analogs for the Performance Assessment of High-level Waste Container Materials, CNWRA 2002-02, Center for Nuclear Waste Regulatory Analyses, 2002, San Antonio, TX
- Tsai, H., Cladding Behavior during Dry Cask Handling and Storage, Nuclear Safety Research Conference, October 20 – 22, 2003, Washington, D.C.
- U. S. Department of Energy, Technical Basis Document No. 7: In-Package Environment and Waste Form Degradation and Solubility, Revision, Bechtel SAIC, 2004, Las Vegas, NV
- U. S. Department of Energy, Yucca Mountain Science and Engineering Report Rev.1, DOE/RW-0539, 2002
- Wilson, C., Results from NNWSI Series 3 Spent Fuel Dissolution Tests, PNL-7170, Pacific Northwest Laboratory, Richland, Washington, 1990